

AD-A110 136


TEXAS UNIV AT AUSTIN DEPT OF CHEMISTRY  
PHOTOELECTROSYNTHESIS AND PHOTOCATALYSIS AT SEMICONDUCTOR ELECT-ETC(U)  
AUG 81 A J BARD  
N00014-78-C-0592

F/G 20/12


UNCLASSIFIED TR-18

ML

1 x 1  
A1 2 4 G

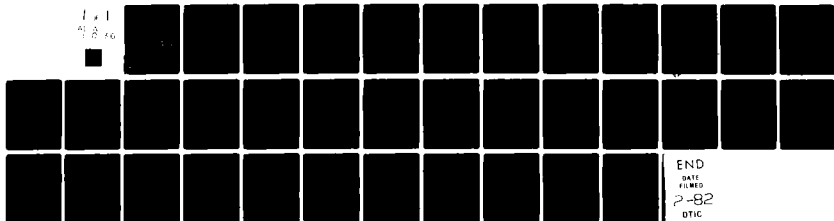

END  
DATE  
FILMED  
7-82  
DTIC

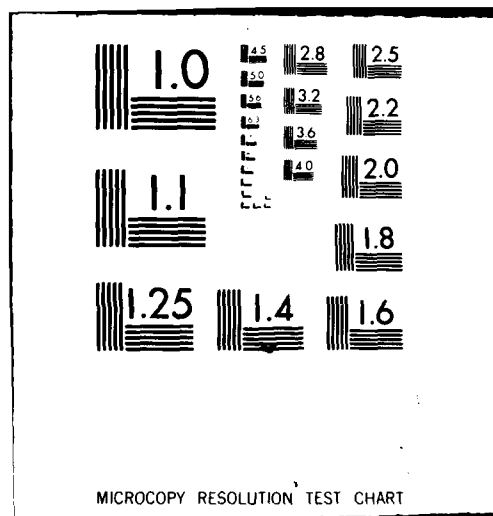

AD A110136

12

LEVEL

OFFICE OF NAVAL RESEARCH

Contract N00014-78-C-0592

Task No. NR 051-693

TECHNICAL REPORT No. 18

PHOTOELECTROSYNTHESIS AND PHOTOCATALYSIS

AT SEMICONDUCTOR ELECTRODES

by

Allen J. Bard

Prepared for Publication

in the

Proceedings of the Sweden Symposium

DTIC  
ELECTE  
JAN 27 1982  
B

The University of Texas at Austin  
Department of Chemistry  
Austin, Texas 78712

August 1, 1981

Reproduction in whole or in part is permitted for  
any purpose of the United States Government.

This document has been approved for public release  
and sale; its distribution is unlimited.

347830

01 26 82 018

DTIC FILE COPY

REPORT DOCUMENTATION PAGE		READ INSTRUCTIONS BEFORE COMPLETING FORM
1. REPORT NUMBER 18	2. GOVT ACCESSION NO. AD-A110936	3. RECIPIENT'S CATALOG NUMBER
4. TITLE (and Subtitle) Photoelectrosynthesis and Photocatalysis at Semiconductor Electrodes		5. TYPE OF REPORT & PERIOD COVERED 9/1/80-8/31/81
7. AUTHOR(s) Allen J. Bard		6. PERFORMING ORG. REPORT NUMBER
9. PERFORMING ORGANIZATION NAME AND ADDRESS Department of Chemistry University of Texas at Austin Austin, TX 78712		8. CONTRACT OR GRANT NUMBER(s) N00014-78-C-0592
11. CONTROLLING OFFICE NAME AND ADDRESS Office of Naval Research 800 N. Quincy Arlington, VA 22217		10. PROGRAM ELEMENT, PROJECT, TASK AREA & WORK UNIT NUMBERS
14. MONITORING AGENCY NAME & ADDRESS (if different from Controlling Office)		12. REPORT DATE August 1, 1981
		13. NUMBER OF PAGES 38
		15. SECURITY CLASS. (of this report) Unclassified
		15a. DECLASSIFICATION/DOWNGRADING SCHEDULE
16. DISTRIBUTION STATEMENT (of this Report) This document has been approved for public release and sale; its distribution is unlimited.		
17. DISTRIBUTION STATEMENT (of the abstract entered in Block 20, if different from Report)		
18. SUPPLEMENTARY NOTES Prepared for publication in the Proceedings of the Sweden Symposium.		
19. KEY WORDS (Continue on reverse side if necessary and identify by block number)		
20. ABSTRACT (Continue on reverse side if necessary and identify by block number) The principles and applications of semiconductor electrodes in photo-electrochemical (PEC) cells for carrying out useful chemical reactions are described. The factors in the design of efficient and stable systems and semiconductor particulate systems constructed on the basis of PEC cell principles are discussed.		

PHOTOELECTROSYNTHESIS AND PHOTOCATALYSIS

AT SEMICONDUCTOR ELECTRODES

Allen J. Bard

Department of Chemistry

The University of Texas


Austin, Texas U.S.A.

(ABSTRACT)

The principles and applications of semiconductor electrodes in photoelectrochemical (PEC) cells for carrying out useful chemical reactions are described. The factors in the design of efficient and stable systems and semiconductor particulate systems constructed on the basis of PEC cell principles are discussed.

-----

Accession For	
WHS	<input checked="checked" type="checkbox"/>
WHS	<input type="checkbox"/>
WHS	<input type="checkbox"/>
Availability	
Distribution/	
Availability Codes	
Avail and/or	
Special	
A	



The efficient production of fuels from inexpensive precursors by utilization of solar energy with cheap and stable chemical systems has become the goal of numerous research efforts. Examples of such reactions are the reduction of water (or protons) to  $H_2$  and the reduction of CO to methanol driven by light. Because the effect of light in any system is the creation of electron-hole ( $e^-h^+$ ) pairs, along with the fuel-producing reduction reaction an oxidation reaction must occur. This oxidation reaction must also consume an inexpensive or waste material (e.g., produce oxygen from water), or alternatively produce a substance of some value (e.g.,  $Cl_2$  from  $Cl^-$  oxidation). The model often used for such systems is biological photosynthesis, which utilizes light to produce reduced carbonaceous materials and  $O_2$ . However the field efficiencies of biological systems, in terms of conversion of solar energy to fuel value, is rarely better than 1% and the individual systems do not show long lives (but they are, of course, self-replicating). Man-made photosynthetic fuel-producing systems will have to show at least an order-of-magnitude better efficiency as well as lifetimes of many years.

One approach to the construction of such a system involves the use of photovoltaic cells (e.g., the solid state p/n junction Silicon solar cells) combined with conventional electrochemical cells (e.g. water electrolysis cells). In this paper I will discuss only integral photoelectrochemical systems based on semiconductor materials.

The basic principles and examples of such liquid junction semiconductor devices have been the subject of a number of reviews.<sup>1-5</sup> I will emphasize in this paper the concepts involved in designing photoelectrochemical (PEC) systems, recent work in this area, and some of the problems that still remain.

The general construction of such a system involving a single light absorber is shown schematically in Figure 1. The energetics of the system, in terms of electron energy levels and redox potentials is given in Figure 2. In general the overall reaction involves the following stages:

- (1) Photon capture and  $e^-h^+$  pair formation (1,2).
- (2) Trapping of  $e^-$  and  $h^+$  in rapid chemical reactions (3,5).
- (3) Catalytic formation of final products (4,6) and separation.

Light is captured in the light-absorbing system (1,2) which represents a support material and the sensitizer layer. This could be a metal substrate with a thin layer of semiconductor (e.g.,  $TiO_2$  on Ti), or an organic dye sensitizer on a semiconductor substrate (e.g.,  $Ru(bpy)_3^{2+}$  or ZnPc on  $TiO_2$ ; where bpy is 2,2'-bipyridine and Pc is phthalocyanine). The light-absorbing system serves to convert the incident photons into electron-hole pairs and, frequently, provides a gradient in electrical or chemical potential to cause separation of  $e^-$  and  $h^+$ . Recombination of  $e^-$  and  $h^+$  is also discouraged if they are transferred rapidly to suitable acceptor, A(3), or donor, D(5), molecules. The couple represented by  $A/A^-$  (e.g.,  $MV^{2+}/MV^+$  or  $S_x^{2-}/S^{2-}$ ; where  $MV^{2+}$  is methyl viologen) should have as negative a redox potential as possible, consistent with rapid reaction with the photogenerated electron. It is unlikely that the fuel producing reaction can occur directly at this stage, since these reactions frequently involve multielectron transfers and high energy intermediates. Similarly the  $D/D^+$  couple (e.g.,  $Br^-/Br_2$  or  $Fe^{2+}/Fe^{3+}$ ) should be as positive as possible consistent with rapid reaction of the photogenerated  $h^+$ . As shown in Figure 2 formation

of  $A^-$  and  $D^+$  results in some degradation of the energy of the  $e^-h^+$  pair. The spontaneous electron transfer reaction between  $A^-$  and  $D^+$  must be prevented by keeping them spatially separated or by having them react rapidly in a subsequent step. Similarly any reaction of  $A^-$  with  $h^+$  or  $D^+$  with  $e^-$  represents a loss in efficiency. The reaction of  $A^-$  to form fuel (e.g.,  $H^+ \rightarrow H_2$ ) usually will require a catalyst,  $CAT_R$  (4), which serves to couple the  $A^- \rightarrow A$  and  $H^+$  reduction reactions and provide a surface for adsorbed intermediates. Similarly an oxidation catalyst,  $CAT_O$  (6), will usually be required to couple the  $D^+ \rightarrow D$  and the terminal oxidation (e.g.,  $H_2O \rightarrow O_2$ ) reaction. These catalyzed reactions again represent some degradation of the initial photon energy and again back-reactions (e.g.,  $A^-$  or  $e^-$  with  $O_2$ ) must be prevented. The total energy of the products,  $\Delta G_p^0$ , is less than the energy of the captured photon, given by the band gap of the light-absorber,  $E_g$ , by the needed driving forces (or overpotentials) of the various electron transfer steps. Thus if  $\Delta G_p^0$  is  $\sim 1.3$  eV (representative of many fuel-forming reactions) and each electron transfer step involves a  $\sim 0.2$  eV overpotential, then  $E_g$  must be greater than 2.1 eV.

#### Principles of Semiconductor Electrodes

The principles of semiconductor electrodes as applied to photo-electrochemical cells have been discussed in a number of reviews<sup>1-7</sup> and will only be outlined here. Basically a space charge layer forms at the semiconductor/liquid interface as the two phases come into electronic equilibrium (i.e., as the Fermi levels or electrochemical potentials become equal) (Figure 3). The electric field in this space charge region serves to separate the  $e^-h^+$  pairs produced by light absorption. The



direction of the field is usually such that holes move to the surface at n-type semiconductors and lead to oxidations while electrons move to the surface at p-type semiconductors and cause reductions. The primary energetics of the system can be obtained from a knowledge of the flat-band potential (which approximately corresponds to the location of the conductor band edge,  $E_c$ , in n-type semiconductors and the valence band edge,  $E_v$ , in p-type) and the band-gap energy,  $E_g$ . Typical values for n-TiO<sub>2</sub> and p-GaAs are shown in Figure 3. However for a given semiconductor, the location of these energy levels depends upon the nature of the solvent, the presence of ions which adsorb on or react with the semiconductor surface, and the presence of surface states or surface charge which leads to pinning or inversion. However, at least as a first approximation, it is useful to consider that under irradiation holes and electrons are delivered at potentials corresponding to  $E_v$  and  $E_c$ , respectively. A PEC cell with a single absorbing semiconductor system and a metal or carbon counter electrode thus can represent the general system of Figure 1 with  $e^-h^+$  separation driven by the electric field in the space charge region and spacial separation of products preventing back reaction.

#### Design of Semiconductor PEC Cells

The design of a practical photoelectrosynthetic cell (a PEC cell which converts radiant energy to chemical free energy) is based on both semiconductor and solution properties.

1. Band-gap energy. The value of  $E_g$  should be as small as possible consistent with driving the desired overall cell reaction. The maximum efficiency for terrestrial solar energy utilization occurs for a  $E_g$  of 1.1 to 1.3 eV, although values up to ~2.0 eV can be used with reasonable efficiencies.<sup>8</sup>

2. Band edge locations. The values of  $E_c$  and  $E_v$ , as represented by the corresponding redox levels, must be compatible with the desired half reactions ( $A/A^-$  and  $D^+/D$ ). The location of these levels depend upon the inherent work function of the semiconductor, but also upon the nature of the solvent and specific adsorption of ionic charge at the interface.

3. Stability. Both the thermodynamic and kinetic factors involved in stability of the semiconductor have been discussed.<sup>9,10</sup> The problem appears more acute with n-type materials where the photogenerated holes which move to the interface are capable of oxidizing the semiconductor itself. For example, with ZnO in an aqueous solution at pH = 0 the half-reaction  $ZnO + 2h^+ \rightarrow Zn^{2+} + \frac{1}{2} O_2$  ( $E_D^0 = +0.9$  V vs. NHE) can occur readily with holes produced at the potential of the valence band edge ( $\sim 3.0$  V vs. NHE). Thus irradiation of a ZnO electrode in an aqueous solution will cause at least partial decomposition of the semiconductor electrode. A number of approaches have been taken to stabilize the semiconductor. By proper choice of the  $D^+/D$  couple the photogenerated hole can be removed rapidly before decomposition can occur. If the standard potential of the  $D^+/D$  couple is below  $E_D^0$ , a direct attack by  $D^+$  on the semiconductor is thermodynamically possible, however. It also appears that a thin layer of metal or conductive polymer on the electrode surface may serve to remove the photogenerated charge rapidly and stabilize the material.<sup>11</sup> If the solvent is changed to a nonaqueous one or the water activity is greatly decreased,  $E_D^0$  can be made more positive and the stability enhanced. Experiments are also under way on the modification of semiconductor surfaces, e.g. by derivitization or polymer coating techniques, in attempts at improving stability.<sup>12,13</sup>

Although p-type materials can be reduced by the photogenerated electrons brought to the electrode surface (e.g. p-Cu<sub>2</sub>O in aqueous electrolytes), in general they tend to be more stable than n-type and are, in fact, self-cathodically protected from oxidation.<sup>14</sup>

4. Doping level. The thickness of the space charge layer and the resistance of the bulk semiconductor are controlled by the doping level. This can be adjusted so that the space charge layer extends sufficiently deep that essentially all of the light is absorbed within it. Higher doping of the bulk semiconductor is desirable, and n<sup>+</sup>n or p<sup>+</sup>p structures can be used to optimize efficiencies.

5. Crystallinity. From the standpoint of ease of production and low cost, polycrystalline semiconductor electrodes are needed. These have been prepared by a number of techniques (e.g. chemical vapor deposition, vacuum evaporation, sputtering, electrodeposition) and in many cases show efficiencies approaching those of single crystal materials.

6. Surface treatment. The nature of the semiconductor surface can be an important factor in the efficiency, since surface states can act as e<sup>-</sup>h<sup>+</sup> recombination centers. Thus different etching, chemical pretreatment and surface modification methods have been used to improve the cell performance.

7. Redox couple. The redox couples chosen for A/A<sup>-</sup> and D/D<sup>+</sup> must satisfy a number of requirements. Both forms should be stable as well as highly soluble (> 1 M) to prevent mass transport control of the current. The heterogeneous electron transfer rates should be rapid and the redox potentials appropriate to drive the desired final fuel-producing reaction at the catalyst and yet be located where photodriven charge transfer and stabilization of the semiconductor occur. They should be inexpensive and neither form should absorb light of energy below E<sub>g</sub>.

## Catalysis

Although the conduction band energy of several p-type electrodes (e.g. GaAs, Si) in aqueous electrolytes are at sufficiently negative values that direct reduction of protons to  $H_2$  is thermodynamically possible, the hydrogen evolution reaction does not occur with good efficiency under illumination. This can be attributed to the slow reaction kinetics for hydrogen evolution at most electrode materials; in electrochemical terminology, most semiconductors show a high hydrogen overpotential. As depicted in Figure 4, formation of hydrogen atoms ( $H\cdot$ ) by the one-electron half-reaction requires a very negative potential. This energy can be overcome if H-atoms are adsorbed, as they are, for example on Pt. The energy of adsorption of  $H\cdot$  on most p-type semiconductors is apparently small. As was demonstrated with both p-GaAs<sup>15</sup> and p-Si,<sup>16</sup> the use of the rapid one-electron redox couple  $MV^{2+}/MV^+$  and finely divided Pt promotes photo-generated hydrogen evolution. The Pt plays the role of a catalyst, and allows the pooling of electrons so that the electron transfer reactions  $2 H^+ + 2 e \rightarrow H_2$  and  $MV^+ \rightarrow MV^{2+} + e$  can both occur at equal rates. An electrochemical model for this catalyzed electron transfer has recently been described.<sup>17</sup>



Oxygen evolution directly at semiconductors (e.g. n-TiO<sub>2</sub>, n-Fe<sub>2</sub>O<sub>3</sub>, n-SrTiO<sub>3</sub>) has been observed, but the valence band location in these is usually sufficiently positive that formation of the high energy intermediate, hydroxyl radical ( $OH\cdot$ ) appears possible. Indeed, spin trapping experiments demonstrate that at irradiated TiO<sub>2</sub> powders  $OH\cdot$  is formed.<sup>18</sup> The production of O<sub>2</sub> utilizing an appropriate couple,  $D^+/D$ , and/or a heterogeneous catalyst should be possible but has not yet been investigated. As discussed earlier, stability of small band-gap semiconductors with appropriately placed valence band edges (e.g. at  $\sim +1.7$  V vs. NHE at pH = 0 or  $\sim +1.3$  V at pH = 7) may be an important problem.

Other oxidation half-reactions, which are inherently more rapid and occur at less positive potentials, such as  $2 \text{Br}^- \rightarrow \text{Br}_2 + 2 \text{e}$ , may also be of interest. Another possibility is the use of "sacrificial" waste materials. For example, the photo-oxidation of acetate to produce ethane and  $\text{CO}_2$  at n- $\text{TiO}_2$  occurs quite readily,<sup>19</sup> and acetate and other carboxylic acids are fermentation products obtainable from biomass. However, one should note that the overall reaction  $2 \text{CH}_3\text{COOH} \rightarrow \text{C}_2\text{H}_6 + \text{CO}_2 + \text{H}_2$  occurs with  $\Delta G^\circ < 0$ , i.e. is thermodynamically downhill, so that the PEC cell reaction is really a photocatalytic (rather than an energy-storing photoelectrosynthetic) one.


#### Particulate Systems

The principles of semiconductor PEC cells can be applied to the design of particulate or powder systems for carrying out photoreactions.<sup>1,2</sup> For example, platinized  $\text{TiO}_2$  powder represents a short circuited photocell analogous to that of Figure 3. Light impinging on the  $\text{TiO}_2$  again causes  $\text{e}^-\text{h}^+$  pair formation and the Pt again appears to serve as an effective reduction site. While there have been few studies on the detailed mechanisms and physical-chemical nature of photoreactions at semiconductor powders in solution, a number of different photoreactions, including metal depositions, decarboxylations, polymerizations, and even small amounts of amino acid synthesis have been demonstrated.<sup>1,2</sup> Reduction of  $\text{CO}_2$  to methanol and other reduced species on irradiated  $\text{TiO}_2$ , CdS, and GaP powders has also been reported,<sup>20</sup> although the overall efficiency for this reaction is quite low. An electrochemical model can again be proposed for photoprocesses on semiconductor powders (Figure 5). An alternative, more chemical, way of looking at photoprocesses is as follows. Consider a  $\text{TiO}_2$  particle. The  $\text{e}^-\text{h}^+$  pair formed near the surface on irradiation

forms, at least transiently, oxidized and reduced sites on the surface. Spin trapping experiments<sup>18</sup> and the results of a number of photochemical studies (e.g. the formation of hydroxylated products during irradiation of benzene and benzoic acid) strongly indicate that the primary  $h^+$ -trapping step is formation of hydroxyl radical. The nature of the reduced site is less certain. However, Ti(III) species in solution have been identified during irradiation of  $TiO_2$  powders in the presence of oxalate ion,<sup>22</sup> and this may represent the primary reduced species. The formation of a lattice  $O_2^{\cdot-}$  species also appears possible from gas phase studies of irradiated  $TiO_2$ <sup>23</sup> and spin trapping<sup>19</sup> experiments. Thus the process can be written, in chemical terms, as:



Subsequent reactions of the oxidized and reduced forms lead to recombination or to the final products. Surface catalysts can promote these secondary reactions, e.g.,



The powder systems are of interest because they are inexpensive and relatively easy to fabricate. They do not offer the large spacial separation of the initially-produced oxidized and reduced forms of the PEC cells and the final products from particulate systems are formed as a mixture rather than in separate streams. There are numerous studies of photo-reactions at powders under way and new physical methods of characterizing the photoprocesses in solution (e.g. photoelectrophoretic and electro-chemical measurements),<sup>24</sup> as well as powerful microscopic and spectroscopic methods of examining the powders in vacuum, are emerging.

### The State-of-the-Art and the Future

The solar power efficiency of most photoelectrosynthetic systems with no input of external electrical energy is generally about 1-2% in terms of fuel value of products out vs. solar energy in. Photoassisted processes, where an electrical bias is applied to the PEC cell and both radiant and electrical energy are used to produce products, show higher efficiencies but are of less interest from a practical viewpoint. These photoelectrosynthetic efficiencies are 5 to 10 times smaller than those obtainable with liquid junction photovoltaic cells. Improvements in performance and practical cell construction require consideration of the following:

1. Energetics. As discussed in the introduction, consideration of the driving forces needed to carry out a fuel-producing reaction suggest that an  $E_g \geq 2.1$  eV is required. This value is outside the range of maximum efficiency of solar energy utilization and can be contrasted to the smaller band-gap materials used in photovoltaic cells (e.g. GaAs and InP;  $E_g = \sim 1.3$  eV) where output voltage (usually  $< 0.6$  V) is not a major factor. A suggested approach to the more effective utilization of solar energy is a dual light absorbing system, depicted in Figure 6. In this case the needed energy can be obtained from two small band gap semiconductors ( $E_g \sim 1.3$  eV) (Figure 7). While two photons are now required in this system to drive a single electron through the redox chain, the smaller band gaps allow a much better match to the solar spectrum. The light absorbing systems could be two n-, two p-, or an n- and p-type semiconductors utilizing the O/R redox pair to couple to the two systems. An alternative approach is the use of n- and p-type materials connected with an ohmic junction ("photochemical diodes") to couple two photons into the overall chemical reaction.<sup>25</sup>

In particulate systems involving such dual light absorbers, special pains will have to be taken to avoid "short-circuiting" reactions of the intermediate redox species from greatly reducing the efficiency. One approach may be the immobilization of some of the redox couples on the surfaces within polymer layers.

An important apparent problem in the energetic analysis described above is the existence of "Fermi level pinning."<sup>26</sup> Briefly, it appears that surface states within the semiconductor band gap, if present at a high enough density, can pin the Fermi level in the semiconductor at a value that is less than the total gap energy. For example with both p-Si and p-GaAs maximum photovoltages of only ~0.6 V are obtained in liquid junction photocells. This would imply that larger band gap materials may be required to drive the desired reactions. A positive aspect of Fermi level pinning is that the semiconductor band edges can be moved with respect to solution redox energy levels to carry out reactions which would not appear possible by consideration only of the semiconductor electrode energetics in the solution in the absence of redox couples. Surface treatments to decrease the extent of Fermi level pinning may be possible.

2. Kinetics. Recombination of the initially formed  $e^-h^+$  pair, as well as intermediates on particulate systems, decrease the efficiency. The extent of recombination can be decreased by improving the kinetics of removal of  $e^-$  and  $h^+$  to form final products. There is some evidence that surface states and grain boundaries can act as recombination centers and methods of passivating these by specific chemical treatment have been proposed.<sup>27</sup>

3. Stability. A key problem appears to be stability of the small band gap semiconductors to the reactive intermediates, e.g. those in the



oxygen-evolution reaction, or to the very positive redox couples ( $D^+/D$ ) needed to drive the oxidation. Various approaches, such as covering the surface with a passivating or polymer layer or employing surface modification are under investigation. The rapid removal of photogenerated charge and reactive intermediates by use of a catalyst on the electrode surface also promotes semiconductor stability. Another approach involves the use of larger band gap and stable semiconductors, e.g.  $TiO_2$ , and a sensitizer layer (e.g. an organic dye,  $Ru(bpy)_3^{2+}$ ,<sup>28-30</sup> metal phthalocyanine<sup>31</sup>) to allow the utilization of lower energy radiation. A number of examples of sensitized processes at semiconductors have been described, however, so far the observed efficiencies have been rather low because thin sensitizer layers do not absorb sufficient quantities of light and thicker layers tend to be resistive. In some cases, recombination processes within the sensitizer layers and dye stability also appear to be problems. However, this approach, particularly with particle systems, is still under active investigation.<sup>32,33</sup>

### Conclusions

About a decade has passed since Honda and Fujishima<sup>34</sup> suggested that PEC cells based on single crystal n-type  $TiO_2$  might be used for the photodecomposition of water to  $H_2$  and  $O_2$ . During this period much has been established about the behavior of the semiconductor/liquid interface and many new materials have been investigated. Particulate systems have been devised and a number of different photocatalytic and photoelectro-synthetic methods have been developed. While the goal of an efficient and stable system for the direct solar production of fuels remains an elusive one, semiconductor-based systems remain the most efficient chemical systems described so far for such reactions. Moreover, research in photoelectrochemistry

has provided new insight into a variety of processes (electrochemical, photographic, catalytic, photolytic). With the efforts under way in a number of academic and industrial laboratories throughout the world, semiconductor/liquid junction systems continue to show great promise as devices for solar-driven chemical reactions.

#### Acknowledgments

The support of the National Science Foundation (CHE 8000682), the Robert A. Welch Foundation, the Office of Naval Research, and the Solar Energy Research Institute is greatly appreciated.

REFERENCES

1. A. J. Bard, J. Photochem., 10, 50 (1979).
2. A. J. Bard, Science, 207, 139 (1980).
3. A. J. Nozik, Annu. Rev. Phys. Chem., 29, 169 (1978).
4. R. Memming, in Electroanalytical Chemistry, A. J. Bard, Ed., (Dekker, New York, 1979), pp. 1-84.
5. M. Wrighton, Acc. Chem. Res., 12, 303 (1979).
6. H. Gerischer, in Physical Chemistry--An Advanced Treatise, H. Eyring, D. Henderson, W. Jost, Eds. (Academic Press, New York, 1970), pp. 463-542.
7. S. R. Morrison, Electrochemistry at Semiconductor and Oxidized Metal Electrodes (Plenum, New York, 1980).
8. J. R. Bolton, Science, 202, 705 (1978).
9. A. J. Bard and M. S. Wrighton, J. Electrochem. Soc., 124, 1706 (1977).
10. H. Gerischer, J. Electroanal. Chem., 82, 133 (1977).
11. R. Noufi, A. J. Frank, and A. J. Nozik, J. Am. Chem. Soc., 103, 1849 (1981).
12. A. B. Bocarsly, E. G. Walton, and M.S. Wrighton, ibid., 102, 3390 (1980).
13. F. R. Fan, B. Wheeler, R. Noufi and A. J. Bard, unpublished results, 1980-81.
14. F. R. Fan and A. J. Bard, J. Am. Chem. Soc., 102, 3677 (1980).
15. F. R. Fan, B. Reichman and A. J. Bard, J. Am. Chem. Soc., 102, 1488, (1980).
16. D. C. Bookbinder, N. S. Lewis, M. G. Bradley, A. B. Bocarsly, and M. S. Wrighton, J. Am. Chem. Soc., 101, 7721 (1979).

17. D. Miller, A. J. Bard, G. McLendon, and J. Ferguson, ibid., in press.
18. C. D. Jaeger and A. J. Bard, J. Phys. Chem., **83**, 3146 (1979).
19. B. Kraeutler and A. J. Bard, J. Am. Chem. Soc., **99**, 7729 (1977);  
Nouv. J. Chim., **3**, 31 (1979).
20. T. Inoue, A. Fujishima, S. Konishi, K. Honda, Nature (London), **277**,  
637 (1979); M. Halman, Nature, **275**, 115 (1978).
21. I. Izumi, F. R. Fan and A. J. Bard, J. Phys. Chem., **85**, 218 (1981).
22. W. W. Dunn and A. J. Bard, submitted for publication.
23. See e.g., G. Munuera, A. R. Gonzalez-Elipé, J. Soria, and J. Sanz,  
J. C. S. Faraday I, **76**, 1535 (1980) and references therein.
24. W. W. Dunn, Y. Aikawa, and A. J. Bard, J. Am. Chem. Soc., in press.
25. A. J. Nozik, Appl. Phys. Lett., **30** 567 (1977).
26. A. J. Bard, A. B. Bocarsly, F. R. Fan, E. G. Walton and M. S. Wrighton,  
J. Am. Chem. Soc., **102**, 3671 (1980).
27. B. A. Parkinson, A. Heller and B. Miller, Appl. Phys. Lett., **33**,  
521 (1978).
28. W. D. K. Clark and N. Sutin, J. Am. Chem. Soc., **99**, 4676 (1977).
29. H. Gerischer, Photochem. Photobiol., **16**, 243 (1972), and references  
therein.
30. M. Gleria and R. Memming, Z. Phys. Chem. (Frankfurt am Main), **98**,  
303 (1975).
31. C. D. Jaeger, F. R. Fan and A. J. Bard, J. Am. Chem. Soc., **102**,  
2592 (1980); A. Giraudeau, F. R. Fan and A. J. Bard, ibid., 5137 (1980).
32. F. R. Fan and A. J. Bard, J. Am. Chem. Soc., **101**, 6139 (1979).
33. E. Borgarello, J. Kiwi, E. Pelizzetti, M. Visca and M. Gratzel,  
Nature, **289**, 158 (1981).
34. A. Fujishima and K. Honda, Bull. Chem. Soc. Jpn., **44**, 1148 (1971);  
Nature (London), **238**, 37 (1972).

### Figure Captions

Figure 1 - Schematic diagram of system for utilization of solar energy in a photoelectrosynthetic reaction (e.g.  $\text{H}_2\text{O} \rightarrow \text{H}_2 + \frac{1}{2} \text{O}_2$ ). 1 and 2 represent the light-absorbing system and support; the dashed line around 1 and 2 represents a possible stabilizing layer on the system. 3 and 5 are redox couples, either in solution or incorporated onto the surface of the system; they act as the primary electron and hole acceptors. The final reaction is catalyzed by oxidation and reduction catalysts,  $\text{CAT}_\text{O}$  and  $\text{CAT}_\text{R}$ , respectively.

Figure 2 - Representative energetics for the system in Figure 1. The numbers at the energy levels represent potentials in V vs. NHE for the reactions at pH = 0. These potentials would shift by  $\sim 0.059$  V per pH unit at 25 °C, so that at pH = 7, they would be about 0.4 V more negative.

Figure 3 - Schematic representation of (A) n-type semiconductor photochemical cell with typical values for the band edge locations for n-TiO<sub>2</sub> at pH = 0 (V vs. NHE). (B) p-type semiconductor cell with band edge locations for p-GaAs at pH = 0.

Figure 4 - Representation of effect of Pt in catalysis of hydrogen evolution reaction. Potentials at pH = 0 in V vs. NHE at right.  $\Delta G_\text{ads}$  is the energy of adsorption of H-atoms on Pt. The relative location of the  $\text{H}^+$  to  $\text{H}\cdot$  and  $\text{H}_2$  levels depends upon potential of the particle.


Figure 5 - The application of individual electrode (semiconductor and Pt) current-potential (i-V) curves in the design of photoelectrochemical cells and particulate systems. Curves shown


Figure Captions (cont'd)

are for an n-type semiconductor (e.g. n-TiO<sub>2</sub>) as shown in Figure 3A. The broken lines show the behavior for the oxidation ( $D \rightarrow D^+$ ) and reduction ( $O \rightarrow R$ , e.g. H<sub>2</sub> evolution) at Pt and the solid lines at the irradiated semiconductor. The  $D \rightarrow D^+$  reaction occurs at less positive potentials at the semiconductor because it is driven by light. a is the operating point for a semiconductor/Pt system and b is for the semiconductor alone. The higher currents at the operating point show that the platinized semiconductor should show a high reaction rate.



Figure 6 - Schematic diagram of a solar energy utilization system employing two light-absorbers and requiring two photons (at energies  $h\nu_1$  and  $h\nu_2$ ) to drive one electron through the system. The system is similar to that in Figure 1, except that an intermediate redox couple, O/R, connects the two light absorbing systems.

Figure 7 - Representative energetics for the system in Figure 6. See Figure 2 caption for other information.


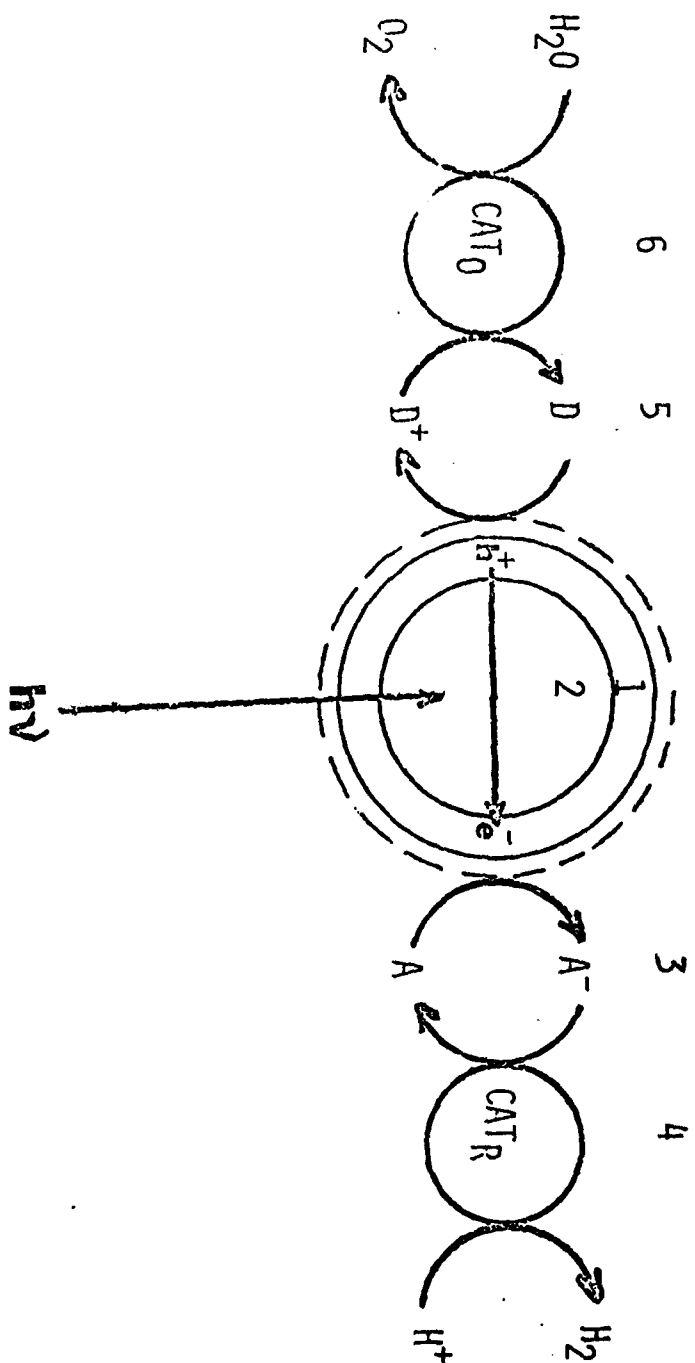


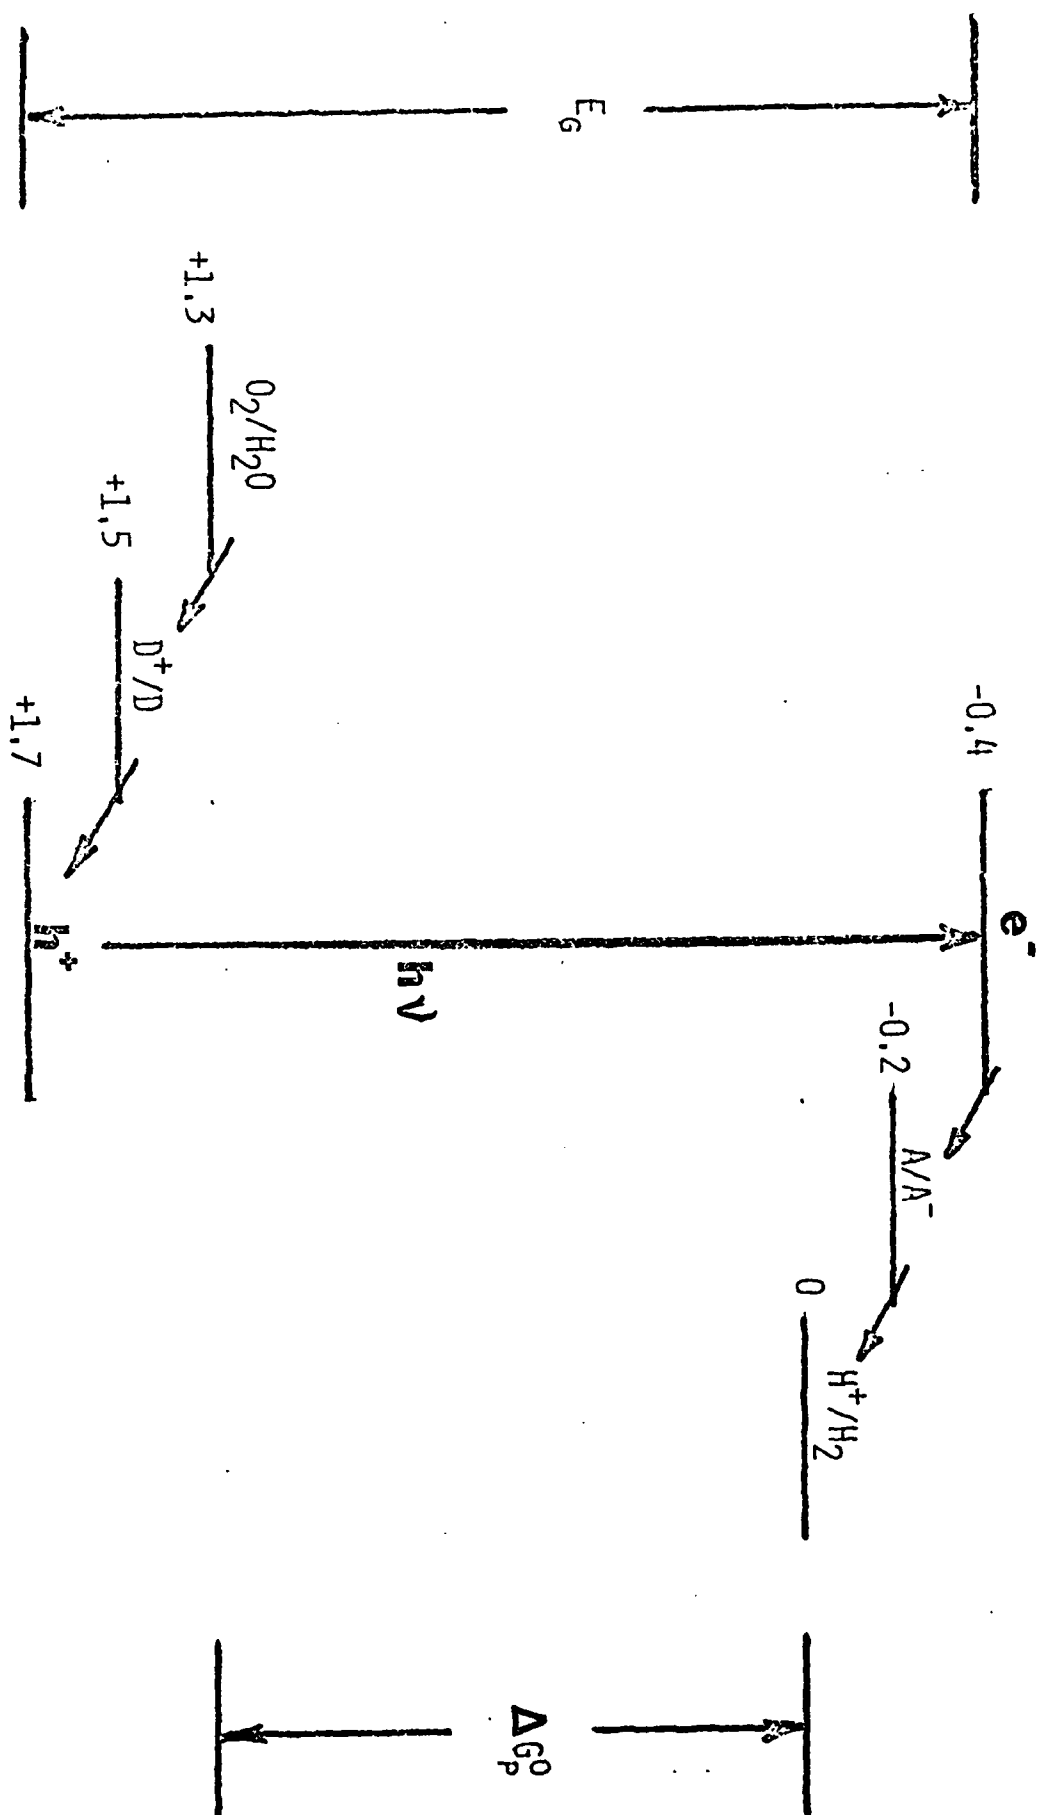



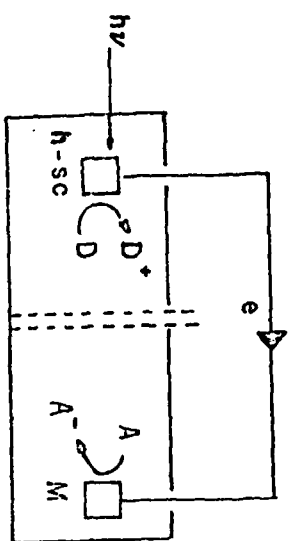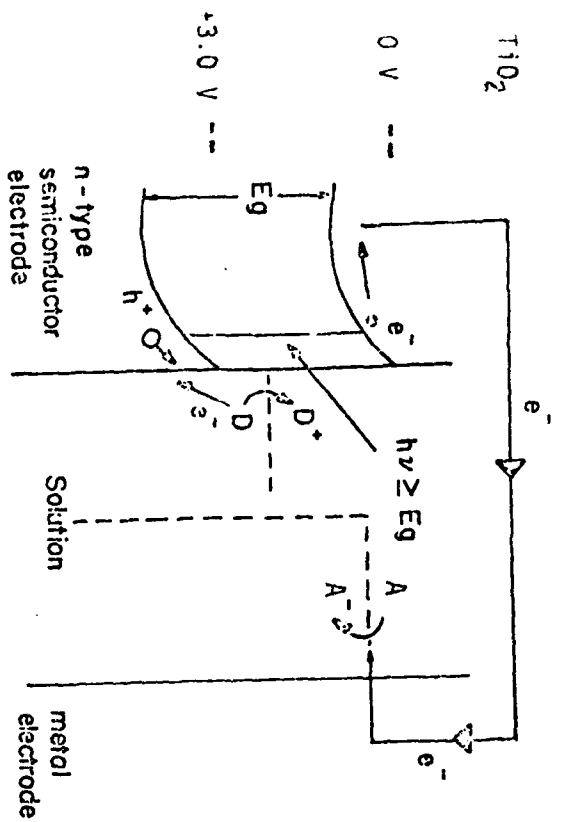

A

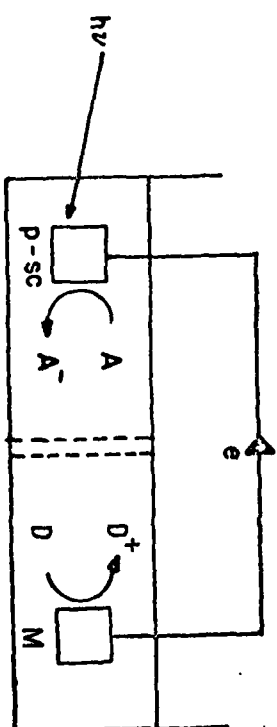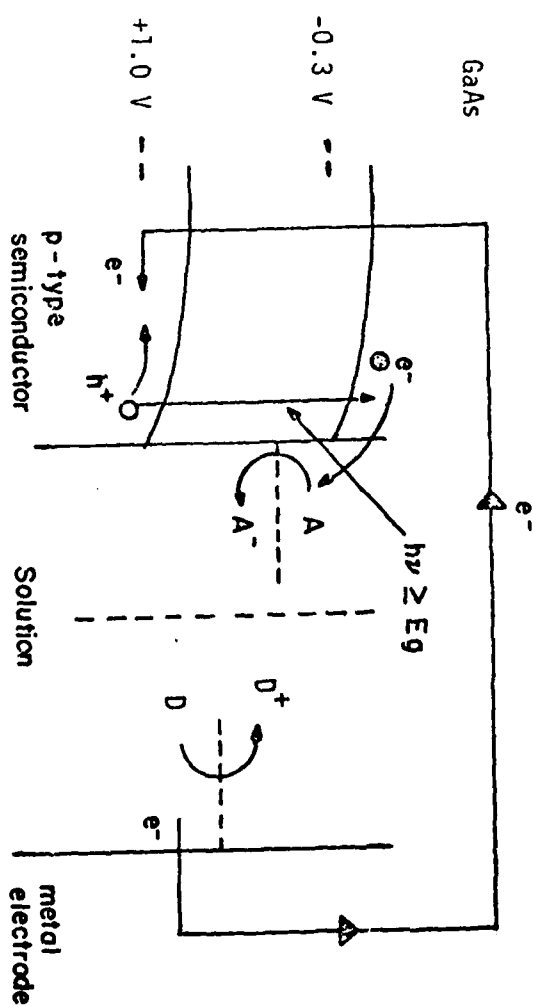

B

H.


$H^+/H.$  -2.1


H.(PT)


$H^+$


$H_2$


$H^+/H_2$  0

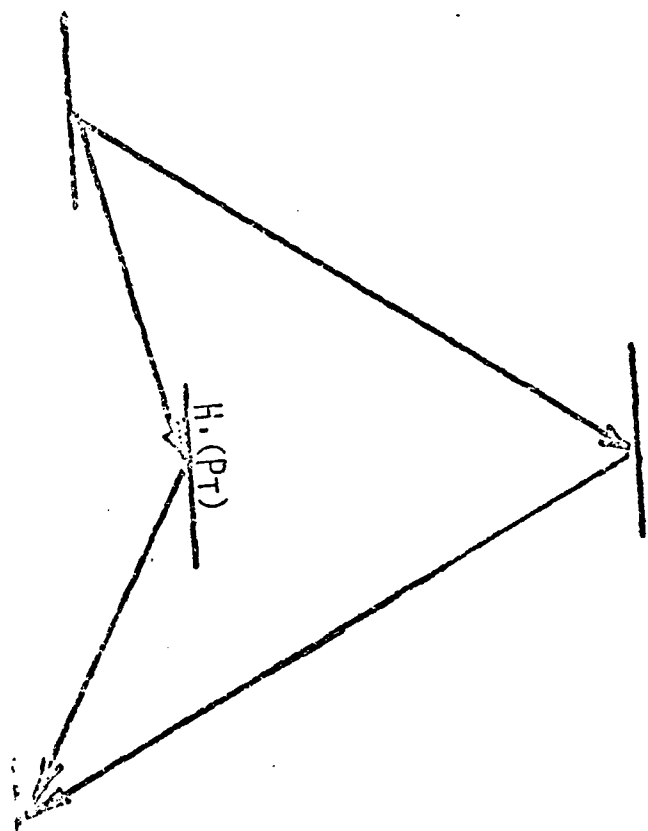


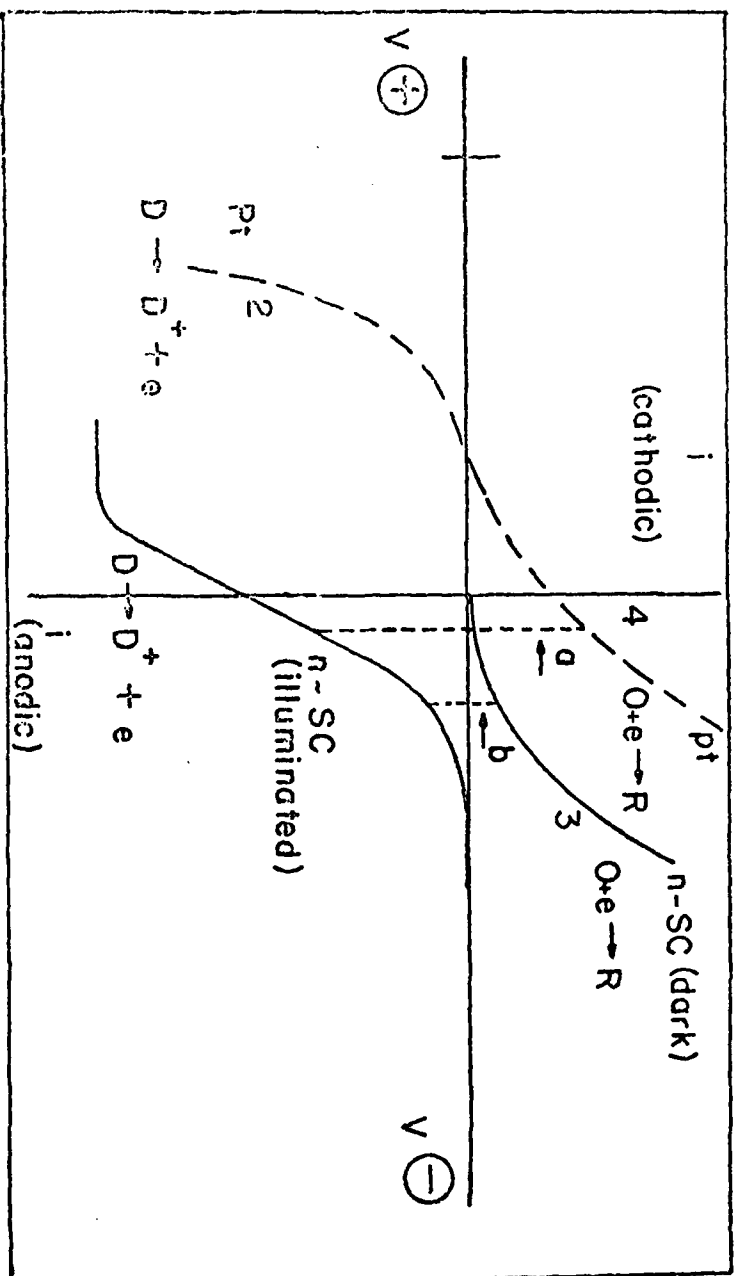


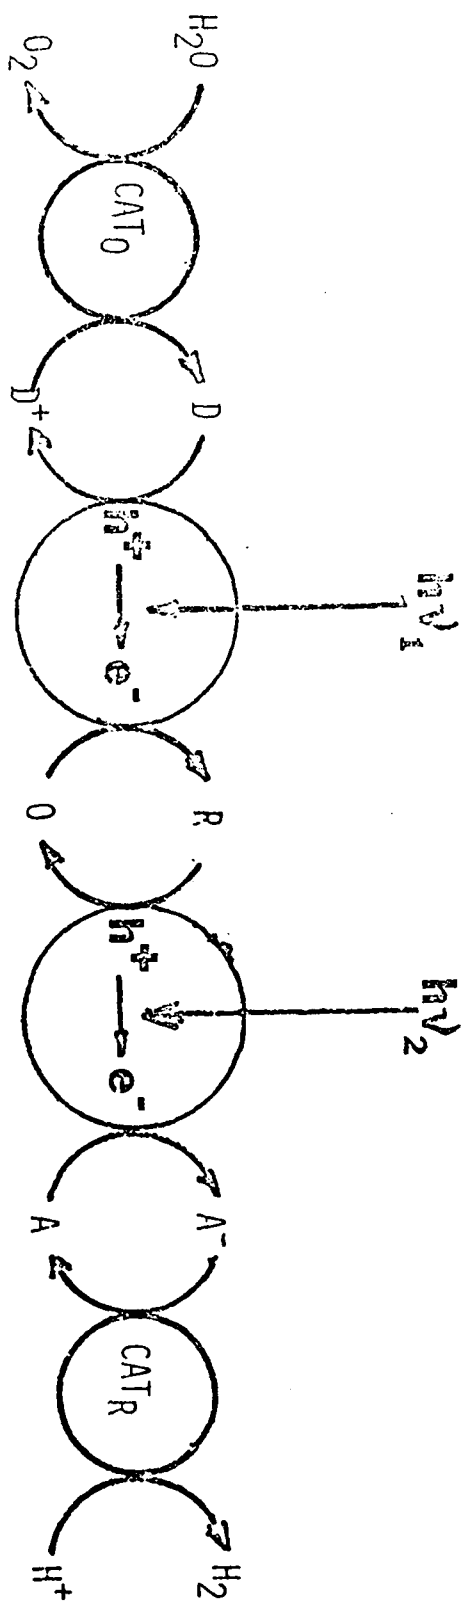

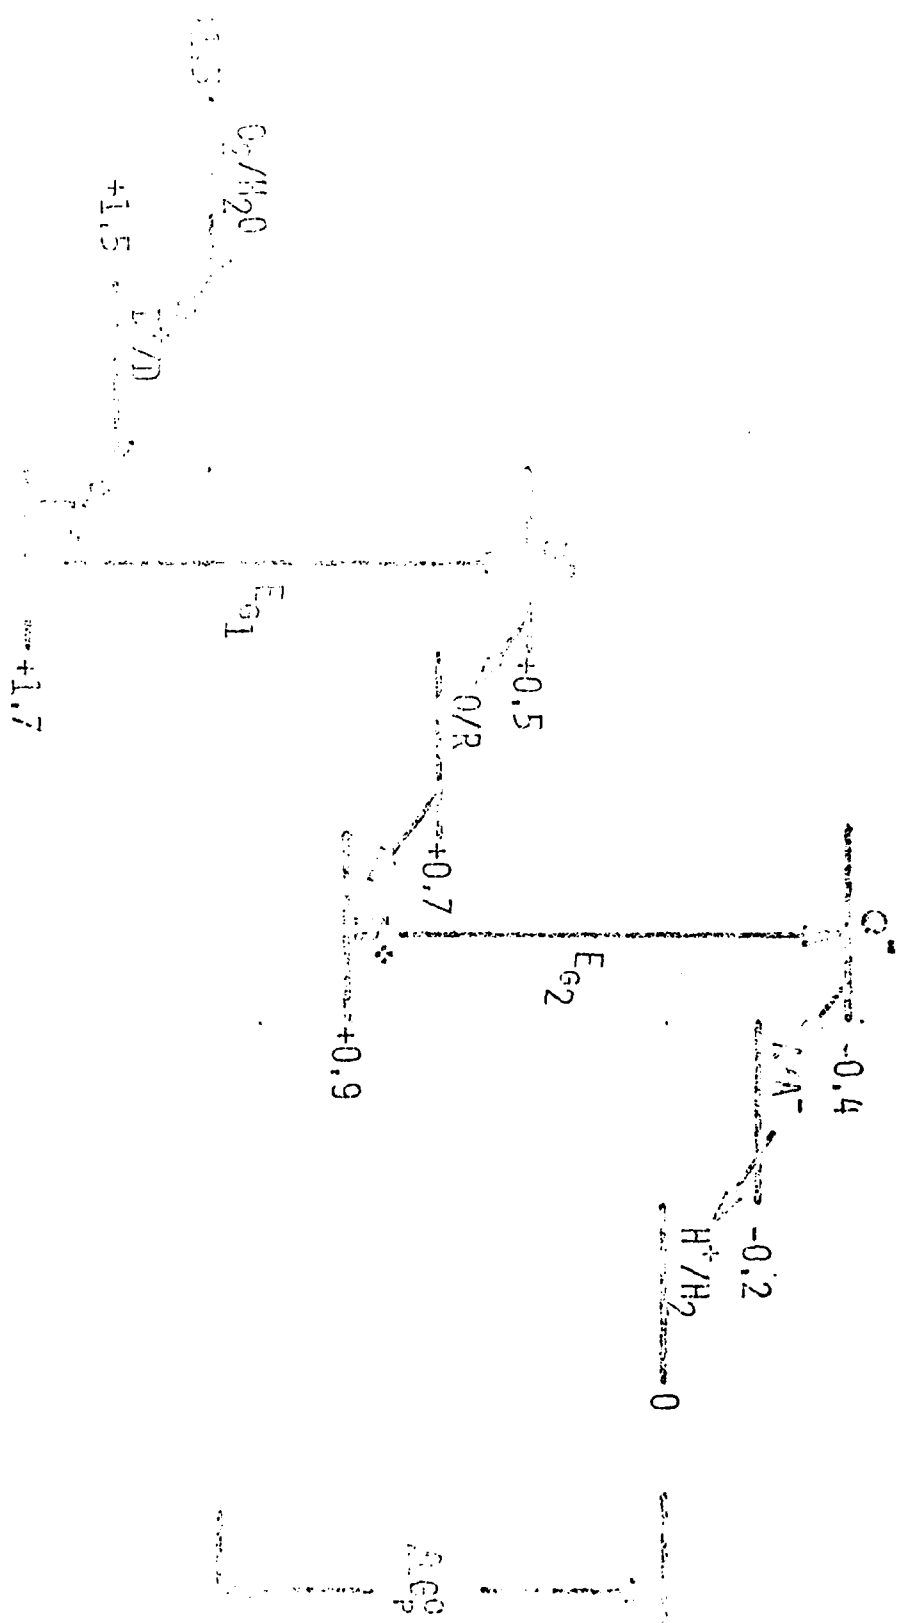


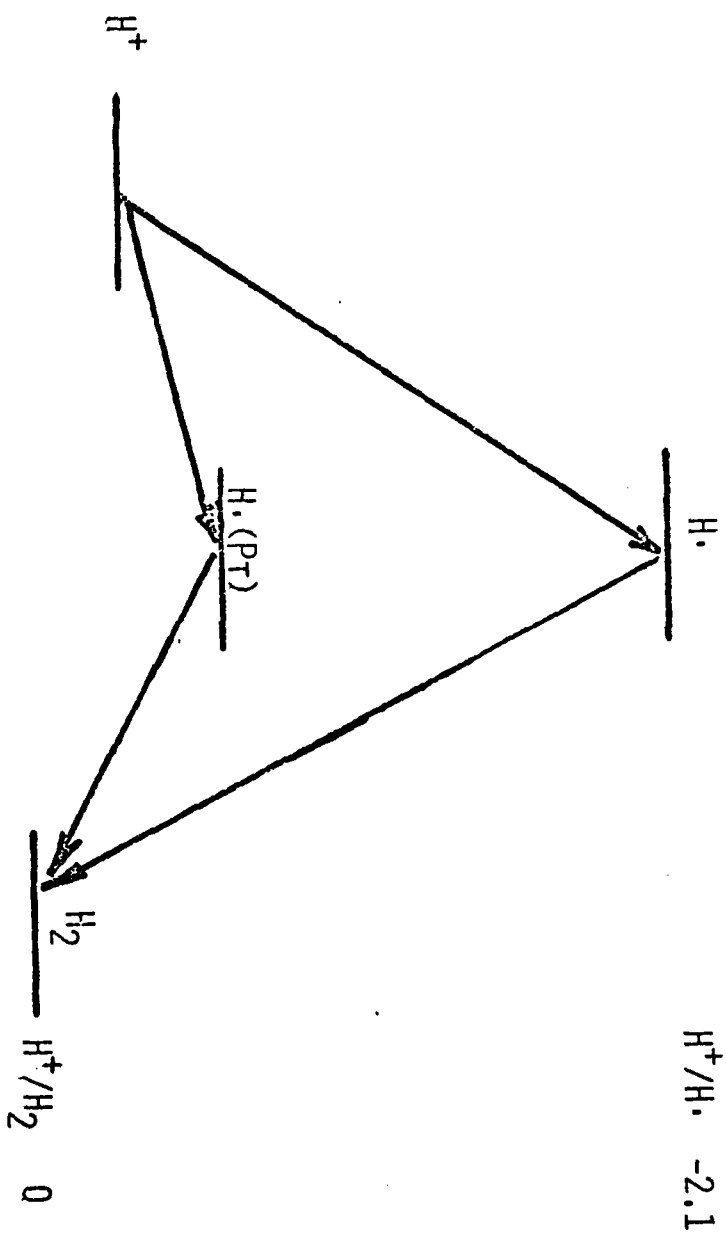


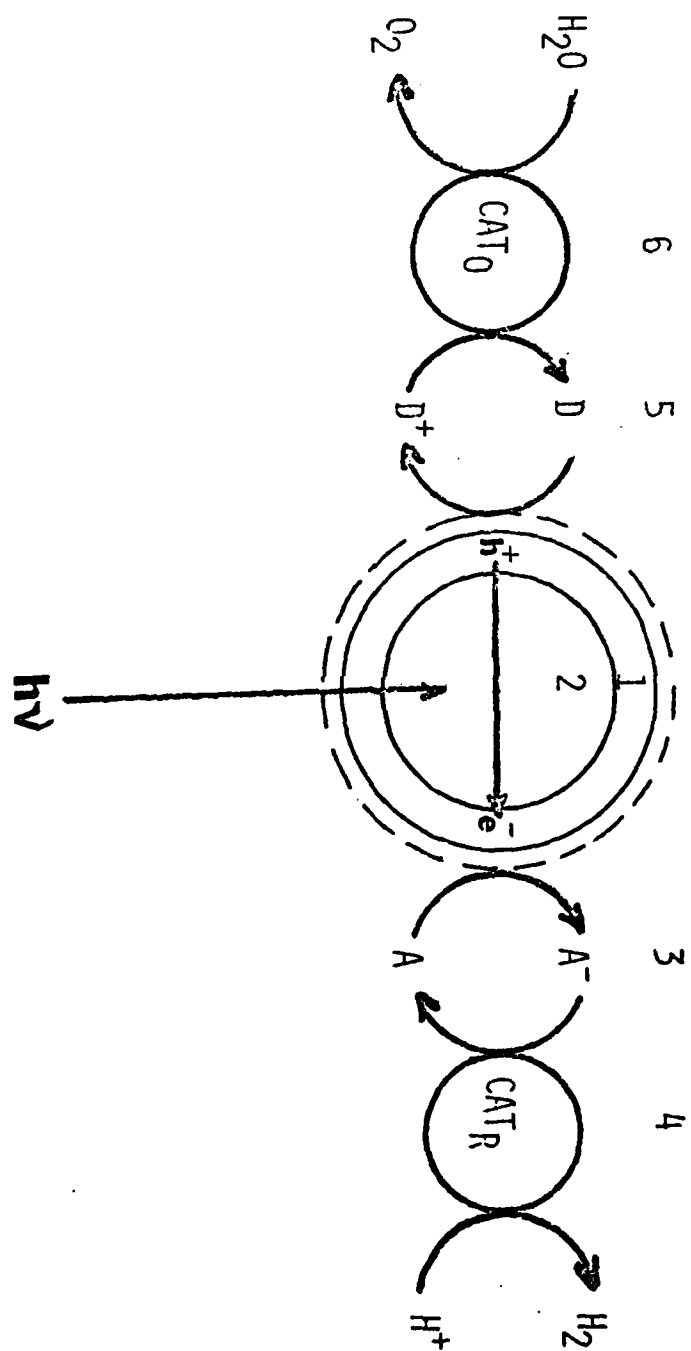

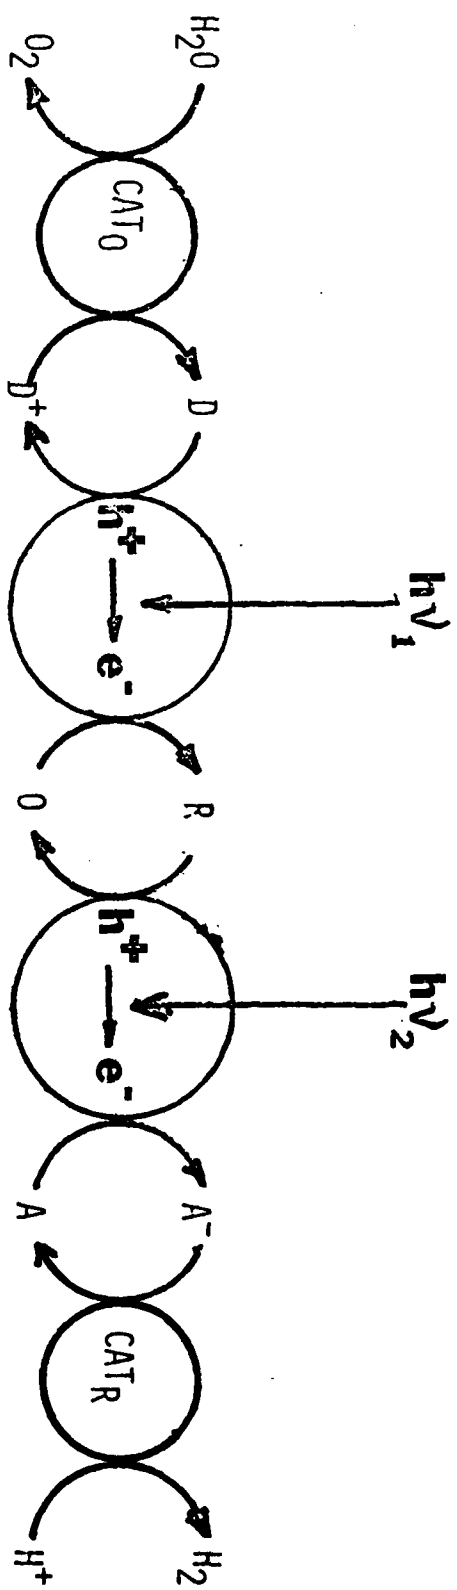



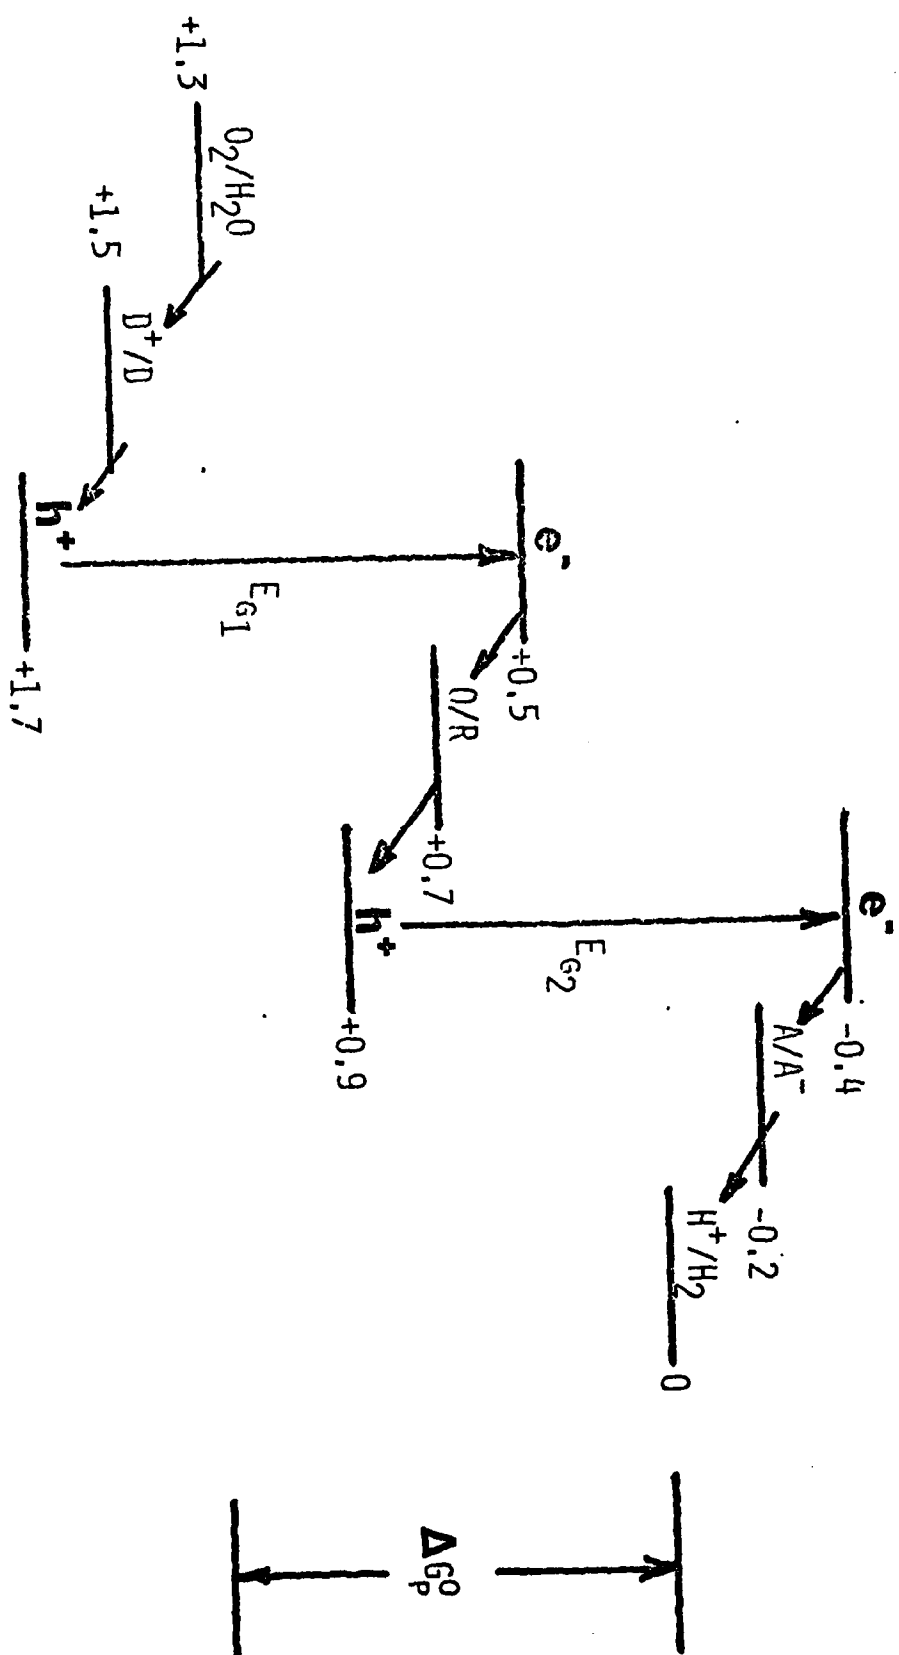

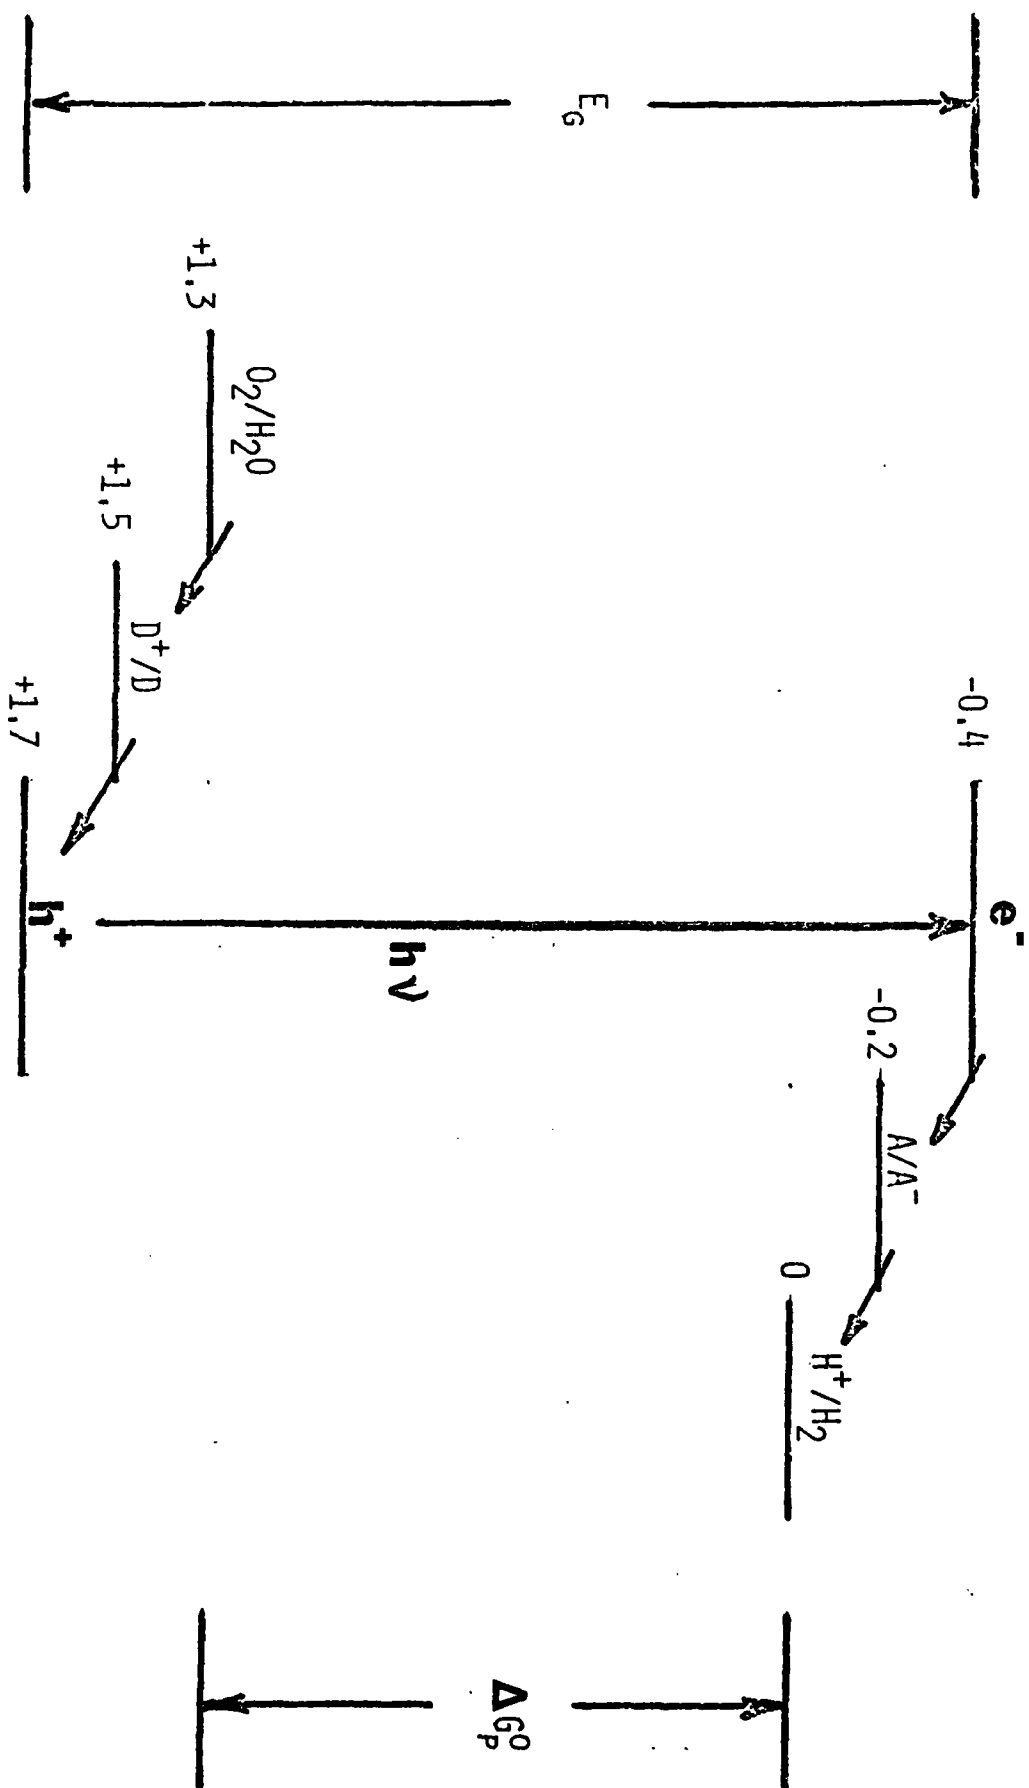

TECHNICAL REPORT DISTRIBUTION LIST, GEN

	<u>No.</u> <u>Copies</u>		<u>No.</u> <u>Copies</u>
Office of Naval Research Attn: Code 472 800 North Quincy Street Arlington, Virginia 22217	2	U.S. Army Research Office Attn: CRD-AA-IP P.O. Box 1211 Research Triangle Park, N.C. 27709	1
ONR Branch Office Attn: Dr. George Sandoz 536 S. Clark Street Chicago, Illinois 60605	1	Naval Ocean Systems Center Attn: Mr. Joe McCartney San Diego, California 92152	1
<del>ONR Area Office -</del> <del>Attn: Scientific Dept.</del> <del>715 Broadway</del> <del>New York, New York 10003</del>	<del>1</del>	Naval Weapons Center Attn: Dr. A. B. Amster, Chemistry Division China Lake, California 93555	1
ONR Western Regional Office 1030 East Green Street Pasadena, California 91106	1	Naval Civil Engineering Laboratory Attn: Dr. R. W. Drisko Port Hueneme, California 93401	1
ONR Eastern/Central Regional Office Attn: Dr. L. H. Peebles Building 114, Section D 666 Summer Street Boston, Massachusetts 02210	1	Department of Physics & Chemistry Naval Postgraduate School Monterey, California 93940	1
Director, Naval Research Laboratory Attn: Code 6100 Washington, D.C. 20390	1	Dr. A. L. Slafkosky Scientific Advisor Commandant of the Marine Corps (Code RD-1) Washington, D.C. 20380	1
The Assistant Secretary of the Navy (RE&S) Department of the Navy Room 4E736, Pentagon Washington, D.C. 20350	1	Office of Naval Research Attn: Dr. Richard S. Miller 800 N. Quincy Street Arlington, Virginia 22217	1
Commander, Naval Air Systems Command Attn: Code 310C (H. Rosenwasser) Department of the Navy Washington, D.C. 20360	1	Naval Ship Research and Development Center Attn: Dr. G. Bosmajian, Applied Chemistry Division Annapolis, Maryland 21401	1
Defense Technical Information Center Building 5, Cameron Station Alexandria, Virginia 22314	12	Naval Ocean Systems Center Attn: Dr. S. Yamamoto, Marine Sciences Division San Diego, California 91232	1
Dr. Fred Saalfeld Chemistry Division, Code 6100 Naval Research Laboratory Washington, D.C. 20375	1	Mr. John Boyle Materials Branch Naval Ship Engineering Center Philadelphia, Pennsylvania 19112	1

TECHNICAL REPORT DISTRIBUTION LIST, 359

	<u>No. Copies</u>		<u>No. Copies</u>
Dr. Paul Delahay Department of Chemistry New York University New York, New York 10003	1	Dr. P. J. Hendra Department of Chemistry University of Southampton Southampton SO9 5NH United Kingdom	1
Dr. E. Yeager Department of Chemistry Case Western Reserve University Cleveland, Ohio 44106	1	Dr. Sam Perone Department of Chemistry Purdue University West Lafayette, Indiana 47907	1
Dr. D. N. Bennion Department of Chemical Engineering Brigham Young University Provo, Utah 84602	1	Dr. Royce W. Murray Department of Chemistry University of North Carolina Chapel Hill, North Carolina 27514	1
Dr. R. A. Marcus Department of Chemistry California Institute of Technology Pasadena, California 91125	1	Naval Ocean Systems Center Attn: Technical Library San Diego, California 92152	1
Dr. J. J. Auborn Bell Laboratories Murray Hill, New Jersey 07974	1	Dr. C. E. Mueller The Electrochemistry Branch Materials Division, Research & Technology Department Naval Surface Weapons Center White Oak Laboratory Silver Spring, Maryland 20910	1
Dr. Adam Heller Bell Laboratories Murray Hill, New Jersey 07974	1	Dr. G. Goodman Globe-Union Incorporated 5757 North Green Bay Avenue Milwaukee, Wisconsin 53201	1
Dr. T. Katan Lockheed Missiles & Space Co, Inc. P.O. Box 504 Sunnyvale, California 94088	1	Dr. J. Boechler Electrochimica Corporation Attention: Technical Library 2485 Charleston Road Mountain View, California 94040	1
Dr. Joseph Singer, Code 302-1 NASA-Lewis 21000 Brookpark Road Cleveland, Ohio 44135	1	Dr. P. P. Schmidt Department of Chemistry Oakland University Rochester, Michigan 48063	1
Dr. B. Brummer FIC Incorporated 55 Chapel Street Newton, Massachusetts 02158	1	Dr. H. Richtol Chemistry Department Rensselaer Polytechnic Institute Troy, New York 12181	1
Library P. R. Mallory and Company, Inc. Northwest Industrial Park Burlington, Massachusetts 01803	1		

TECHNICAL REPORT DISTRIBUTION LIST, 359

	<u>No. Copies</u>		<u>No. Copies</u>
Dr. A. B. Ellis Chemistry Department University of Wisconsin Madison, Wisconsin 53706	1	Dr. R. P. Van Duyne Department of Chemistry Northwestern University Evanston, Illinois 60201	1
Dr. M. Wrighton Chemistry Department Massachusetts Institute of Technology Cambridge, Massachusetts 02139	1	Dr. B. Stanley Pons Department of Chemistry University of Alberta Edmonton, Alberta CANADA T6C 2G2	1
Larry E. Plew Naval Weapons Support Center Code 30736, Building 2906 Crane, Indiana 47522	1	Dr. Michael J. Weaver Department of Chemistry Michigan State University East Lansing, Michigan 48824	1
S. Rubv DOE (STOR) 600 E Street Washington, D.C. 20545	1	Dr. R. David Rauh EIC Corporation 55 Chapel Street Newton, Massachusetts 02158	1
Dr. Aaron Wold Brown University Department of Chemistry Providence, Rhode Island 02192	1	Dr. J. David Margerum Research Laboratories Division Hughes Aircraft Company 3011 Malibu Canyon Road Malibu, California 90265	1
Dr. R. C. Chudacek McGraw-Edison Company Edison Battery Division Post Office Box 28 Bloomfield, New Jersey 07003	1	Dr. Martin Fleischmann Department of Chemistry University of Southampton Southampton SO9 5NH England	1
<del>Dr. A. J. Bard University of Texas Department of Chemistry Austin, Texas 78712</del>	<del>1</del>	Dr. Janet Ostervoung Department of Chemistry State University of New York at Buffalo Buffalo, New York 14214	1
Dr. M. M. Nicholson Electronics Research Center Rockwell International 3370 Miraloma Avenue Anaheim, California	1	Dr. R. A. Osteryoung Department of Chemistry State University of New York at Buffalo Buffalo, New York 14214	1
Dr. Donald W. Ernst Naval Surface Weapons Center Code R-33 White Oak Laboratory Silver Spring, Maryland 20910	1	Mr. James R. Moden Naval Underwater Systems Center Code 3632 Newport, Rhode Island 02840	1

TECHNICAL REPORT DISTRIBUTION LIST, 359

	<u>No.</u> <u>Copies</u>		<u>No.</u> <u>Copies</u>
Dr. R. Nowak Naval Research Laboratory Code 6130 Washington, D.C. 20375	1	Dr. John Kincaid Department of the Navy Strategic Systems Project Office Room 901 Washington, DC 20376	1
Dr. John F. Houlihan Shenango Valley Campus Pennsylvania State University Sharon, Pennsylvania 16146	1	M. L. Robertson Manager, Electrochemical Power Sonices Division Naval Weapons Support Center Crane, Indiana 47522	1
Dr. M. G. Sceats Department of Chemistry University of Rochester Rochester, New York 14627	1	Dr. Elton Cairns Energy & Environment Division Lawrence Berkeley Laboratory University of California Berkeley, California 94720	1
Dr. D. F. Shriver Department of Chemistry Northwestern University Evanston, Illinois 60201	1	Dr. Bernard Spielvogel U.S. Army Research Office P.O. Box 12211 Research Triangle Park, NC 27709	1
Dr. D. H. Whitmore Department of Materials Science Northwestern University Evanston, Illinois 60201	1	Dr. Denton Elliott Air Force Office of Scientific Research Bldg. 104 Bolling AFB Washington, DC 20332	1
Dr. Alan Bewick Department of Chemistry The University Southampton, SO9 5NH England	1		
Dr. A. Himy NAVSEA-5433 NC #4 2541 Jefferson Davis Highway Arlington, Virginia 20362	1		

TECHNICAL REPORT DISTRIBUTION LIST, GENNo.  
Copies

Dr. Rudolph J. Marcus  
Office of Naval Research  
Scientific Liaison Group  
American Embassy  
APO San Francisco 96503

1

Mr. James Kelley  
DTNSRDC Code 2803  
Annapolis, Maryland 21402

1